

The Metal Complexes of Natural Compounds, Usnic Acid and Naringenin Immobilized on Mesoporous Silica: Solid Phase Extraction and Oxidative Catalytic Properties

¹Serhan URUŞ*, ²Ahmet ÇAKIR, ²İbrahim Ethem ULUÇAY and ^{3,4}Ali ASLAN

¹Department of Chemistry, Faculty of Science and Letters, Kahramanmaraş Sütçü İmam University, 46050, Kahramanmaraş, Turkey.

²Kilis 7 Aralık University, Faculty of Science and Letters, Department of Chemistry, 79000-Kilis, Turkey.

³Faculty of Arts and Science, Department of Biology, Kyrgyz-Turkish Manas University, Bishkek, Kyrgyzstan.

⁴Faculty of Pharmacy, Department of Pharmacology, Yüzüncü Yıl University, TR-65080, Campus, Van, Turkey.
serhanurus@yahoo.co.uk*

(Received on 24th December 2020, accepted in revised form 24th May 2021)

Summary: The novel semi-natural Schiff bases were synthesized with the reaction of the natural compounds usnic acid and naringenin extracted and purified in natural sources and chemically modified silica gel. Cu(II), Ni(II), Co(II) and Mn(II) complexes of the ligands were synthesized and the silica-supported ligands and their metal complexes were characterized by FT-IR, TG/DTA, SEM, EDX, ICP-OES and elemental analyses techniques. The solid-phase extraction behaviours of the novel silica-supported ligands were examined. It was found that the hybrid materials showed the very efficient adsorption properties to Cu(II), Cd(II), Pb(II) and Cr(III) metal ions maximum at pH=8-9. The metal ions could be recovered again nearly 100 % from the silica-supported ligands in the recycling experiments. The catalytic efficiencies of the metal complexes in the oxidation reactions of cyclohexane, cyclohexene, cyclooctane and styrene substrates were examined under microwave irradiation in the present of H₂O₂. The complexes showed very good catalytic activities in the oxidation reactions of the various tested substrates.

Keywords: Usnic acid, Naringenin, Schiff base, Silica gel, Solid-phase extraction, Catalysis.

Introduction

The Schiff base ligands which are the Lewis bases can form the stable 4, 5 or 6 coordinated complexes with preferably phenolic-OH groups near the azomethine group with some metal ions [1,2]. The size, charge and ionization potential of metal ions affect the stability of coordination compounds. The structures of coordination compounds of Schiff bases formed with divalent metal ions can be in planar, tetragonal, tetrahedral or octahedral geometries. Ligands surround a metal as a cluster of ions and molecules and are therefore widely used in the preparation of various complexes. Hence, Schiff bases and their metal complexes are widely used in the various areas including catalysis, agriculture, cosmetics, pharmaceuticals and industrial chemistry [1, 2, 11, 12, 3–10]. Schiff bases and coordination compounds have also attracted attention due to their various biological activities such as antibacterial [13], antifungal [8], antiviral [14], insecticidal [15, 16], plant growth regulator [8, 17], antiinflammatory and analgesic [18, 19], antitumoral and cytotoxic [18–21]. Solid phase extraction allows the enrichment and purification of any analytes from a solution via a solid adsorbent. It can be performed as a batch and an elution processes. The process based on the elution of a liquid through a column holding the analytes such as a cartridge, resin or a disc and then recovering the holding analytes with a suitable solvent. In recent years, solid-phase extraction has been widely used

for enriching trace toxic pollutants such as pesticides in water samples [22]. Ion-exchanging resins, chelating polymers and inorganic materials are widely used as support materials in solid-phase extraction. [23] The most important characteristics of an ideal support material are their regular structure, controlled and effective capacity, suitable particle size, chemical and thermal stability. Support materials used in solid phase extraction are water-insoluble solid materials to which bonded ligands or metal complexes [24]. Some of the advantages of inorganic support materials as compared with organic support materials are good mechanical stability, fast retention of metal ions, no swelling, good selectivity [23]. Numerous reports on the adsorption of some microorganisms, natural compounds, metal salts, polymers, chelating organic materials *etc.* using solid supports such as silica gel, metal oxides, zeolites, clay, sand, activated carbon, fibers, cellulose, chitin, chitosan, ion exchange resins has been documented [25, 26]. Aromatic Schiff bases and/or their complexes formed with different metal ions are known to have catalytic activity in oxidation, hydrolysis, electro-reduction and degradation reactions [8]. Catalytic oxidation reactions are the commercially important reactions. More than half of the chemicals produced in commercial catalytic processes are subjected to the catalytic oxidation process as part of their synthesis. Besides, catalytic

*To whom all correspondence should be addressed.

oxidation of environmental and water pollutants are one of the important area [27]. Most of the monomers used in the production of fibers, plastics and other polymer products are produced by the selective oxidation of hydrocarbons using the catalysts containing metal complexes of various ligands [9,10]. In this study, silica gel was preferred as inorganic support material because of its superior properties to other support materials. The aims of the study were a) in order to the chemical modification of the silica gel with 3-aminopropyl-triethoxysilane (APTES); b) in order to synthesize the new ligands of two type of the natural compounds, usnic acid and naringenin; c) to evaluate the solid phase extraction properties of these ligands by syringe technique using Cu(II), Pb(II), Cd(II) and Cr(III) metal ions in aqueous solution; d) in order to synthesize the complexes of Ni(II), Cu(II), Co(II) and Mn(II) on silica-supported semi-natural Schiff bases; e) in order to characterize the chemical structures of the synthesized ligands and their metal complexes via FT-IR, SEM, EDX, ICP-OES, TG/DTA and elemental analysis techniques; f) in order to determine the catalytic oxidation effects of silica-supported Schiff base-metal complexes under microwave power.

Experimental

Chemicals, apparatus, materials and reagents

All the reagents and the organic solvents were purchased from commercial sources and used as received, unless noted otherwise. Naringenin was purchased from Sigma-Aldrich, while usnic acid was isolated from *U. longissima* lichen species. Merck Silica gel 60 having particle size of 0.063-0.200 mm (70-230 mesh) was used as solid support. Infrared spectra were recorded using KBr discs (4000–400 cm^{-1}) on a Perkin Elmer Spectrum 400 FT-IR. Elemental analyses were performed using LECO CHNS 932 instrument. The thermal behavior data of the compounds were collected on a SII Exstar STA 6000 thermal analysis system under nitrogen atmosphere at a heating rate of 10 $^{\circ}\text{C}/\text{min}$ in the range 30-900 $^{\circ}\text{C}$. The surface morphology of the silica-supported ligands were analyzed Zeiss Evo LS10 SEM attached with Bruker Quantax EDS. The amount of metal ions of the metal-complexes were determined by using Perkin Elmer Optima 2100DV ICP-OES coupled with AS93 autosampler after an acid-peroxide digestion in Berghof MWS3+ microwave oven. Calibration standarts of all elements were prepared from Inorganic Ventures individual certified standards (each of 1000 $\text{mg}\cdot\text{L}^{-1}$). Instrument conditions, calibration points and emission wavelengths of the elements were determined

according to the elements. Ultrapure water obtained from a Milli-Q purifier system (Millipore Corp., Bedford, MA) was used throughout the work. The catalytic reaction products were characterized and analyzed by using Perkin Elmer Clarus 600 GC equipped with MS detector fitted with Elite-5 MS and FID detector fitted with BPX5 capillary columns. Calibration standarts were prepared in dichloromethane solvent and injected to gas chromatography. External calibrations were drawn by the instrument software with the obtained data for each substrate and products. Amine modified silica-gel was produced with our previous studies [4–7, 28].

Isolation of usnic acid from Lichen material

Usnea longissima Ach. was collected from the Erzurum-Oltu region (Northern Anatolia) of Turkey in August 2013. It was identified and a voucher specimen (ATA-KKEF-776) has been deposited in the herbarium of Atatürk University, Erzurum (Turkey). The chemical structure of usnic acid was characterized by UV, IR, $^1\text{H-NMR}$ and $^{13}\text{C-NMR}$ and was confirmed based on the previous spectroscopic data [29, 30].

Synthesis of $\text{SiO}_2\text{@APTES-Usnic acid (UA)}$ and $\text{SiO}_2\text{@APTES-Naringenin (NG)}$

Each of usnic acid (5 mmol, 1.72 g) and naringenin (5 mmol, 1.36 g) were mixed the separately to modified silica gel (5 g) in 50 ml of ethanolic mixture and refluxed for 24 h. The ligands ($\text{SiO}_2\text{-APTES-UA}$ and $\text{SiO}_2\text{@APTES-NG}$) were filtered in vacuo, washed with acetone and distilled water, respectively and then dried at 75 $^{\circ}\text{C}$ under vacuum.

$\text{SiO}_2\text{@APTES-UA}$: Yellowish colour. Elemental analysis (%): C, 24.10; H, 2.32; N, 1.86. FTIR (KBr, cm^{-1}): ν ; 3536 (br, Ar-OH), 1621 (br, -C=N), 1557 (br, ArC=C), 1372 (s, -C-N), 1189 (C-O), 1055 (s-br, Si-O), 788 (Si-C).

$\text{SiO}_2\text{-APTES-NG}$: Dark yellow colour. Elemental analysis (%): C, 15.36; H, 2.32; N, 1.93. FTIR (KBr, cm^{-1}): ν ; 3536 (br, Ar-OH), 1635 (br, -C=N), 1593 (br, Ar C=C), ν 1344 (s, -C-N), 1223 (C-O), 1051 (s-br, Si-O), 788(Si-C).

Synthesis of Metal Complexes of $\text{SiO}_2\text{@APTES-UA}$ and $\text{SiO}_2\text{@APTES-NG}$

In order to synthesize $\text{SiO}_2\text{@APTES-UA-M(II)}$ complexes, $\text{SiO}_2\text{@APTES-UA}$ ligand (1g) was

individually mixed 2 mmols of $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$, CuCl_2 , MnCl_2 and $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ in ethanol and refluxed at 65°C for 8 hours. The mixtures was then filtered, washed over acetone and distilled water, respectively, and dried under vacuum.

SiO₂@APTES-UA-Co(II): Green colour. Elemental analysis (%): C, 15.55; H, 2.96; N, 1.58; Co, 4.56. FTIR (KBr, cm^{-1}): ν ; 3453 (br, Ar-OH), 1622 (br, -C=N), 1552 (br, ArC=C), ν 1372 (s, -C-N), 1189 (C-O), 1048 (s-br, Si-O), 788 (Si-C).

SiO₂@APTES-UA-Cu(II): Green colour. Elemental analysis (%): C, 14.96; H, 2.96; N, 1.45; Cu, 4.61. FTIR (KBr, cm^{-1}): ν ; 3453 (br, Ar-OH), 1621 (br, -C=N), 1558 (br, Ar C=C), ν 1370 (s, -C-N), 1187 (C-O), 1051 (s-br, Si-O), 789 (Si-C).

SiO₂@APTES-UA-Mn(II): Brown colour. Elemental analysis (%): C, 15.17; H, 2.81; N, 1.58; Mn, 4.43. FTIR (KBr, cm^{-1}): ν ; 3558 (br, Ar-OH), 1621 (br, -C=N), 1557 (br, ArC=C), ν 1372 (s, -C-N), 1187 (C-O), 1054 (s-br, Si-O), 792 (Si-C).

SiO₂@APTES-UA-Ni(II): Yellow colour. Elemental analysis (%): C, 19.15; H, 2.79; N, 4.82; Ni, 4.55. FTIR (KBr, cm^{-1}): ν ; 3454 (br, Ar-OH), 1622 (br, -C=N), 1557 (br, ArC=C), ν 1372 (s, -C-N), 1189 (C-O), 1053 (s-br, Si-O), 788 (Si-C).

SiO₂@APTES-NG-Co(II): Brown colour. Elemental analysis (%): C, 12.56; H, 2.69; N, 1.56; Co, 4.50. FTIR (KBr, cm^{-1}): ν ; 3556 (br, Ar-OH), 1635 (br, -C=N), 1601 (br, ArC=C), ν 1304 (s, -C-N), 1197 (C-O), 1056 (s-br, Si-O), 788 (Si-C).

SiO₂@APTES-NG-Cu(II): Brown colour. Elemental analysis (%): C, 12.61; H, 2.76; N, 1.63; Cu, 4.65. FTIR (KBr, cm^{-1}): ν ; 3445 (br, Ar-OH), 1634 (br, -C=N), 1602 (br, ArC=C), ν 1311 (s, -C-N), 1199 (C-O), 1057 (s-br, Si-O), 789 (Si-C).

SiO₂@APTES-NG-Mn(II): Brown colour. Elemental analysis (%): C, 13.30; H, 2.47; N, 1.62; Mn, 4.29. FTIR (KBr, cm^{-1}): ν ; 3444 (br, Ar-OH), 1635 (br, -C=N), 1594 (br, ArC=C), ν 1311 (s, -C-N), 1217 (C-O), 1059 (s-br, Si-O), 795 (Si-C).

SiO₂@APTES-NG-Ni(II): Brown colour. Elemental analysis (%): C, 12.93; H, 2.50; N, 2.25; Ni, 3.94. FTIR (KBr, cm^{-1}): ν ; 3526 (br, Ar-OH), 1635 (br, -C=N), 1598 (br, ArC=C), ν 1309 (s, -C-N), 1209 (C-O), 1051 (s-br, Si-O), 789 (Si-C).

Solid Phase Extraction Properties of SiO₂@APTES-UA and SiO₂@APTES-NG

The solid phase extraction properties of SiO_2 @APTES-UA and SiO_2 @APTES-NG towards Cu (II), Pb (II), Cd (II) and Cr (III) ions in water samples were examined by using syringe method as applied our previous studies [4, 7, 28].

Catalytic Oxidation

Oxidation experiments were carried according to our previous study [6].

Results and Discussion

Syntheses

In the first step of the synthesis, silica gel surface was activated to form silanol groups (Si-OH) and 3-aminopropyl-triethoxysilane (APTES) compound was bonded to chemical modification of silica gel. In the second step of the study, usnic acid and naringenin were chemically bound into the modified silica gel to form the Schiff base. The last, Ni(II), Cu(II), Co(II) and Mn(II) complexes of the silica-supported Schiff bases were synthesized and characterized by FT-IR, SEM, EDX, ICP-OES, TG/DTA and elemental analysis techniques (Fig.1).

FT-IR

Some of the peaks of the functional groups can be observed intensive enough due to the predominance of the silica gel in FT-IR spectra. Another problem is that silica gel is fastly absorbs too much moisture and water often close the vibration bands of compound bonded to silica gel [31]. Vibrations of the silica-supported usnic acid and naringenin ligands and their metal complexes were observed enough (Fig S1). C=C bands of aromatic ring were seen as very weak around $1585\text{-}1600\text{ cm}^{-1}$, whereas the vibration bands of aromatic -OH groups were observed as weak peaks around $3450\text{-}3550\text{ cm}^{-1}$. The stretch of azomethine group (CH=N) were collected around $1620\text{-}1635\text{ cm}^{-1}$. C-N, C-O, Si-O and Si-C vibrations were determined around 1350 cm^{-1} , 1200 cm^{-1} , 1050 cm^{-1} and $780\text{-}800\text{ cm}^{-1}$, respectively in the fingerprint region of the FT-IR spectra. All data are consistent with the previous reports [5-7,32] and the elemental analysis results and important FT-IR signals of the ligands and their metal complexes are presented in Table-1

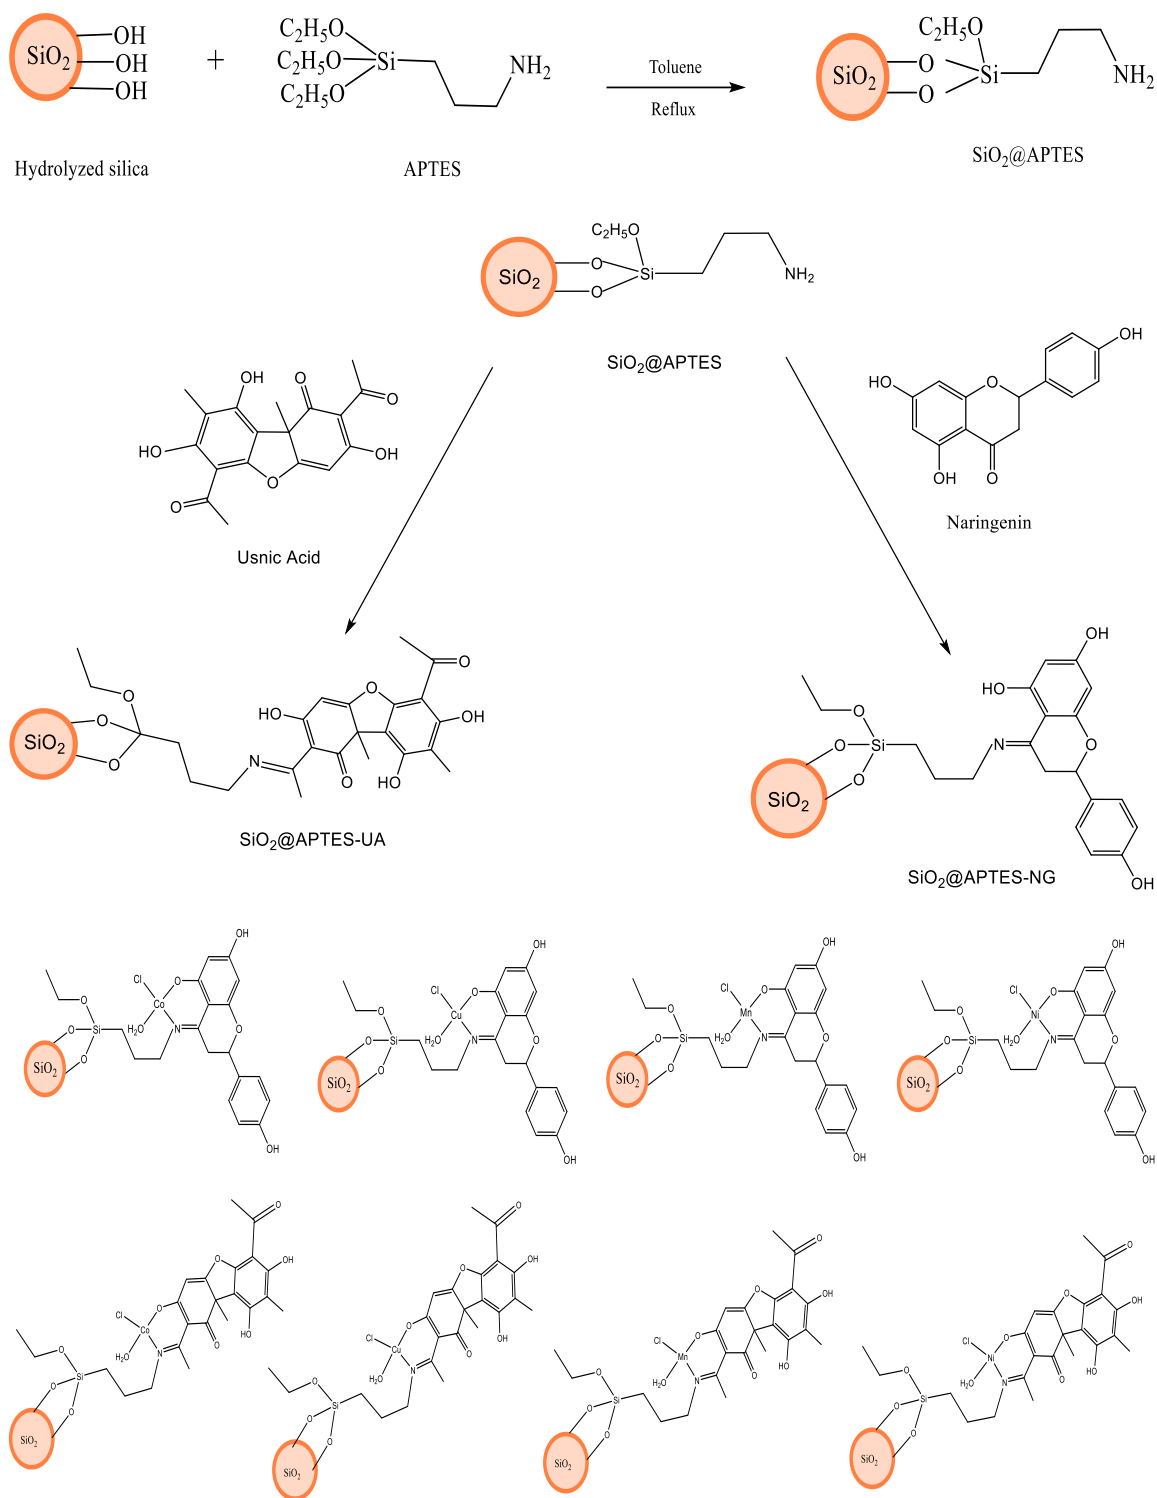


Fig. 1: Synthesis of $\text{SiO}_2\text{@APTES-UA}$ and $\text{SiO}_2\text{@APTES-NG}$ and the possible structures of the synthesized $\text{SiO}_2\text{@APTES-UA-M(II)}$ and $\text{SiO}_2\text{@APTES-NG-M(II)}$ complexes.

Table-1:Elemental Analysis results and significant FT-IR signals of the ligands and their metal complexes.

	N %	C %	H %	Metal %	v(-OH)	v(C=C)	v(C=N)	v(C-O)	v(C-N)	v(Si-O)	v(Si-C)
SiO ₂ @NG	-	-	-	-	3536	1593	1635	1223	1344	1051	788
SiO ₂ @NG-Co(II)	1.56	12.56	2.69	4.50	3556	1601	1635	1197	1304	1056	788
SiO ₂ @NG-Mn(II)	1.62	13.30	2.47	4.29	3444	1594	1635	1217	1311	1059	795
SiO ₂ @NG-Cu(II)	1.63	12.61	2.76	4.65	3445	1602	1634	1199	1311	1057	789
SiO ₂ @NG-Ni(II)	2.25	12.93	2.50	3.94	3526	1598	1635	1209	1309	1051	789
SiO ₂ @UA	-	-	-	-	3536	1557	1621	1189	1372	1055	788
SiO ₂ @UA-Co(II)	1.58	15.55	2.96	4.56	3553	1552	1622	1189	1372	1048	788
SiO ₂ @UA-Mn(II)	1.58	15.17	2.81	4.43	3558	1557	1621	1187	1372	1054	792
SiO ₂ @UA-Cu(II)	1.45	14.96	2.96	4.61	3453	1558	1621	1187	1370	1051	789
SiO ₂ @UA-Ni(II)	4.82	19.15	2.79	4.55	3454	1557	1622	1189	1372	1053	788

NG: Naringenin; UA: Usnic acid

Thermogravimetric Properties (TG/DTA)

According to TG/DTA analyses (Fig S2), the thermal characteristics of SiO₂@APTES-UA, SiO₂@APTES-NG ligands and their metal complexes are very similar. The main difference is the new band due to the formation of metal oxide forms after the degradation of organic groups in metal complexes. In general, two or three endothermic bands were observed in TG/DTA curves of the silica gel-supported imine ligands. All the metal complexes have lost a small amount of physical adsorbed water with an endothermic band between 25-80 °C. This band is thought to be formed by desorption of adsorbed water prior to TGA analysis due to the hygroscopic structure of silica gel. In TG/DTA analysis, the bands observed up to 200 °C are estimated to be due to the water molecules coordinated to the metal complexes. Endothermic peaks ranging from 200 to 700 °C were observed as big band including the degradation of organic backbone and coordinated groups and the formation of metal oxides [1,3,6,28].

SEM/EDX

SEM images (Fig S3) showed that the surface and gaps of the silica gel particles were coated and the filled with the organic compounds, usnic acid and naringenin. The ligands and their metal complexes dispersed on silica-gel particles played very efficient roles as adsorbents in solid-phase extraction tests and good heterogeneous catalysts in the oxidation reactions. It can be said that the coordinations of chloro ligands to the metal centers were observed at around 2.6 keV in EDX spectra in order to balance ionically for all the complexes. Whereas aqua ligands were attached to the remaining coordination holes of the metals.

Solid Phase Extraction

In the solid phase extraction studies performed by syringe method, pH: 4-10 ranges were studied to determine the effect of pH on the metal ion adsorption. The maximum adsorption was observed in the range of pH: 8-9 (Fig. 2). In the case of pH≤4, imine groups were positively charged due to the acidic environment and therefore, the adsorption of positively charged metal ions was not performed well to the silica-supported adsorbents. In contrast to low pH values, the adsorptions was reduced due to metal-hydroxide formation at pH> 9. Therefore, the optimum pH range was determined as pH: 8-9. The synthesized new solid phases showed very good sorbent properties against Pb (II), Cr (III) and Cu (II) ions [4,7,28,32–34]. Recovery trials are very important for pre-concentration and purification processes, therefore, finding a suitable eluent to recover the adsorbed metal ions is the crucial point for solid phase extraction. For this purpose, HCl (2M) and HNO₃ (2M) solutions were used for the recovery of the metals and the metals recovered with about 100% yield (Table 2). The synthesis of silica-supported SiO₂@APTES-UA and SiO₂@APTES-NG ligands with high yields and high recovery rates in acidic environments indicate that these ligands are more suitable ligands for solid phase extraction [4, 7, 28, 32–34]

Table-2: Effect of different eluents on recovery of the metals ions.

	Elution	Recovery (%)			
		Cu(II)	Cd(II)	Cr(II)	Pb(II)
SiO ₂ @APTES-UA	2M HCl	81.6	73.2	100	100
	2M HNO ₃	97.7	58.7	100	100
SiO ₂ @APTES-NG	2M HCl	100	45.5	100	100
	2M HNO ₃	92	49.9	100	100

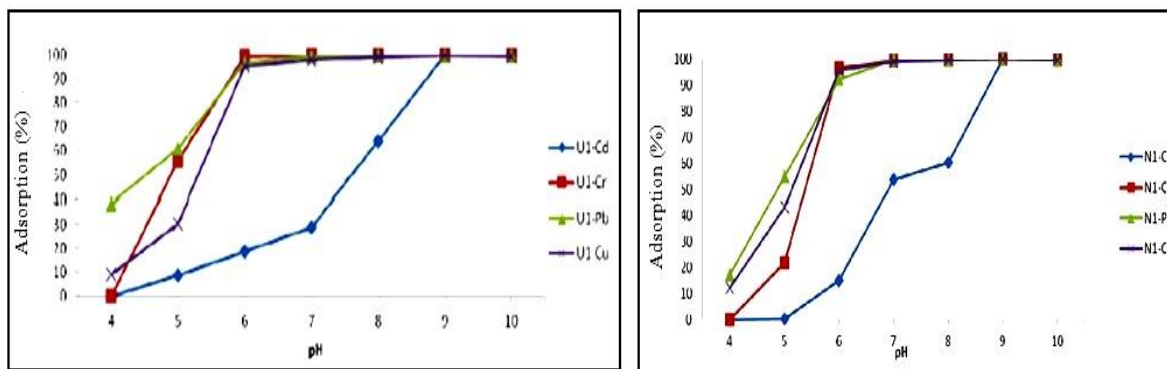


Fig. 2: The effect of pH on adsorption. U1: SiO₂@APTES-UA and N1: SiO₂@APTES-NG.

Table-3: Langmuir and Freundlich isotherm parameters.

	Metal	Langmuir isotherm			Freundlich Isotherm		
		q ₀	b	R ²	n	K _f	R ²
SiO ₂ @APTES-UA	Cr	0,2547	83,8932	0,7247	1,0878	10,7105	0,9997
	Cd	0,0927	245,6036	0,6627	1,1080	9,0733	0,9993
	Cu	0,3509	54,1749	0,9539	1,0398	13,5573	0,9962
	Pb	0,0694	265,1750	0,9067	1,0804	8,8972	0,9998
SiO ₂ @APTES-NG	Cr	0,2040	109,1759	0,8718	1,1106	9,4426	0,9997
	Cd	0,2435	79,5853	0,8628	1,0701	10,9422	0,9998
	Cu	0,0980	234,5287	0,9777	1,0826	9,7653	0,9973
	Pb	0,0970	166,6236	0,7945	1,0549	10,9608	0,9999

The sorption characteristics of SiO₂@APTES-UA and SiO₂@APTES-NG were evaluated with the sorption isotherm models of *Freundlich* and *Langmuir*. The monolayer *Langmuir* and the empirical *Freundlich* isotherms are usually represented in the following linearized forms:

$$\ln q_e = \ln K_f + \frac{1}{n \ln C_e}$$

Langmuir isotherm

$$\frac{C_e}{q_e} = \frac{C_e}{q_0} + \frac{1}{q_0 b}$$



Freundlich isotherm;

q_e is the amount of solute sorbed on the surface of the sorbent (mmol/g), C_e is the equilibrium ion concentration in the solution (mmol/L), q_0 is the maximum surface density at monolayer coverage and b is the Langmuir adsorption constant (L/mmol), K_f is the Freundlich constant (mmol/g) which indicates the sorption capacity and represents the strength of the absorptive bond and n is the heterogeneity factor which represents the bond distribution. The fit of a model to the experimental data are usually evaluated in terms of linear regression coefficients where R^2 value is used as an indication for the benefit of model fit [24, 25, 27, 35, 42-46]. The linear fittings of the Langmuir isotherm model are shown in Table-3. R^2

values indicate that the Langmuir isotherm fits the experimental data better than the Freundlich model for adsorption studies. The fact shows that the mechanisms for the two adsorbents are monolayer adsorption on a homogenous surface and chemisorptions.

Catalytic Oxidation Under Microwave Power

The optimized reaction parameters such as substrate:catalyst ratio, oxidant amount, temperature, pressure and catalysis time were applied according to our previous study [6]. The quantitative analyses of the reaction products were performed by GC-FID. In the catalytic oxidation tests, H₂O₂ was used as oxidant at 100 °C in acetonitrile medium in 1.5 h reaction time. The substrate conversion, the yields of the products and the selectivities are shown in the Fig. 4. It can be said that SiO₂@APTES-UA-Co(II) and SiO₂@APTES-NG-Co(II) complexes showed high conversions to products cyclohexanol (Cy-OH) and cyclohexanone (Cy=O) cyclohexane undergoes. Those are very good catalysts in the formation of cyclohexanol with high selectivity (Fig. 4) when compared with literature results [2, 27, 35]. On the other hand, it appears that other metal complexes of SiO₂@APTES-UA and SiO₂@APTES-NG ligands tested catalyze the conversion of cyclohexane significantly whereas their selectivities are found to be very low levels (Fig S5).

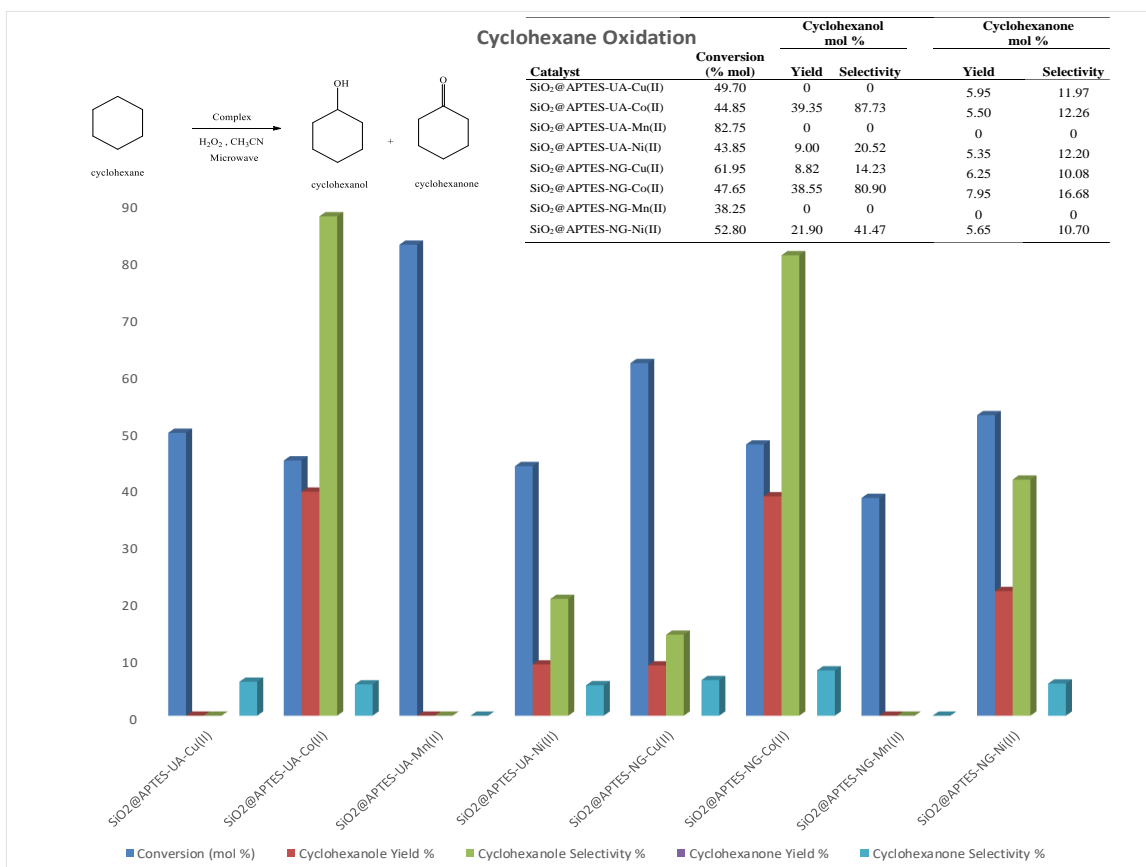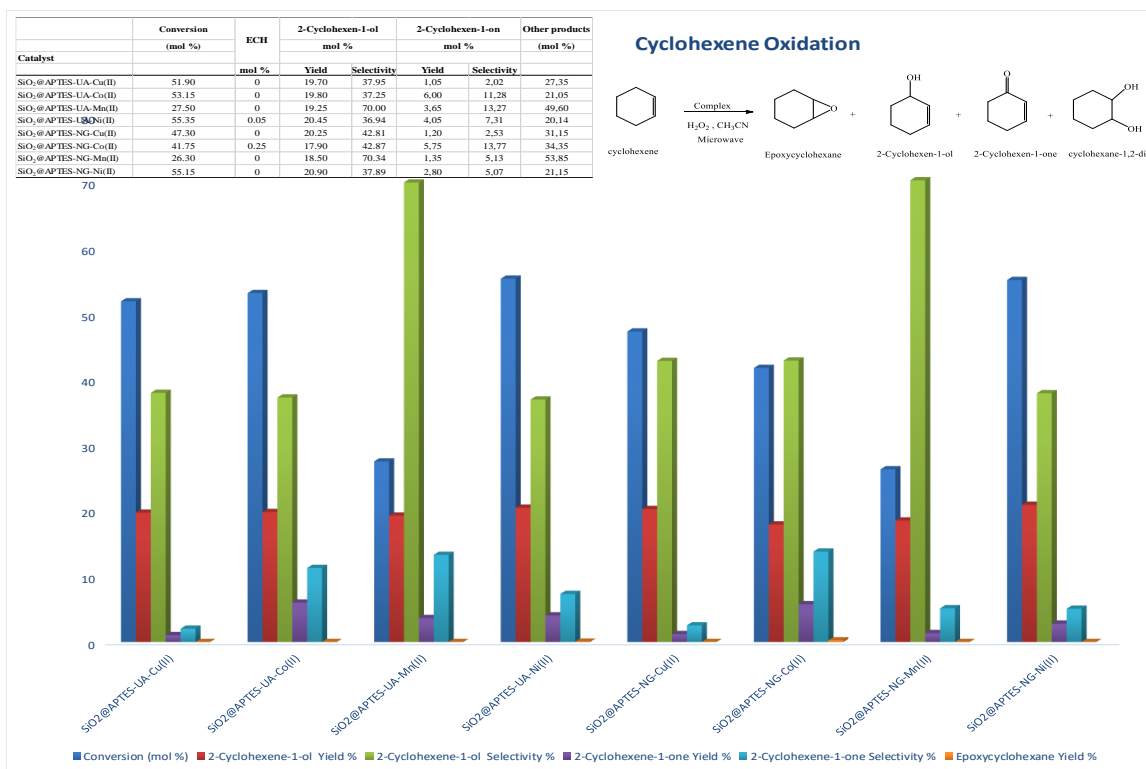

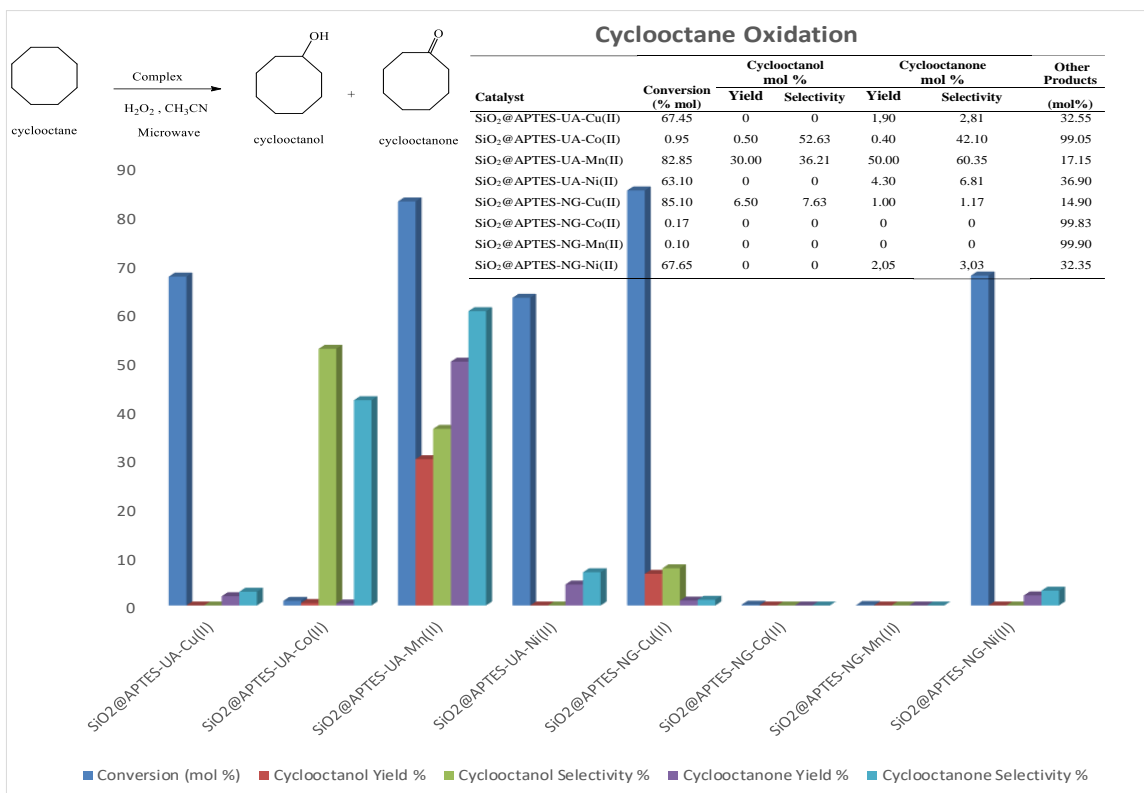
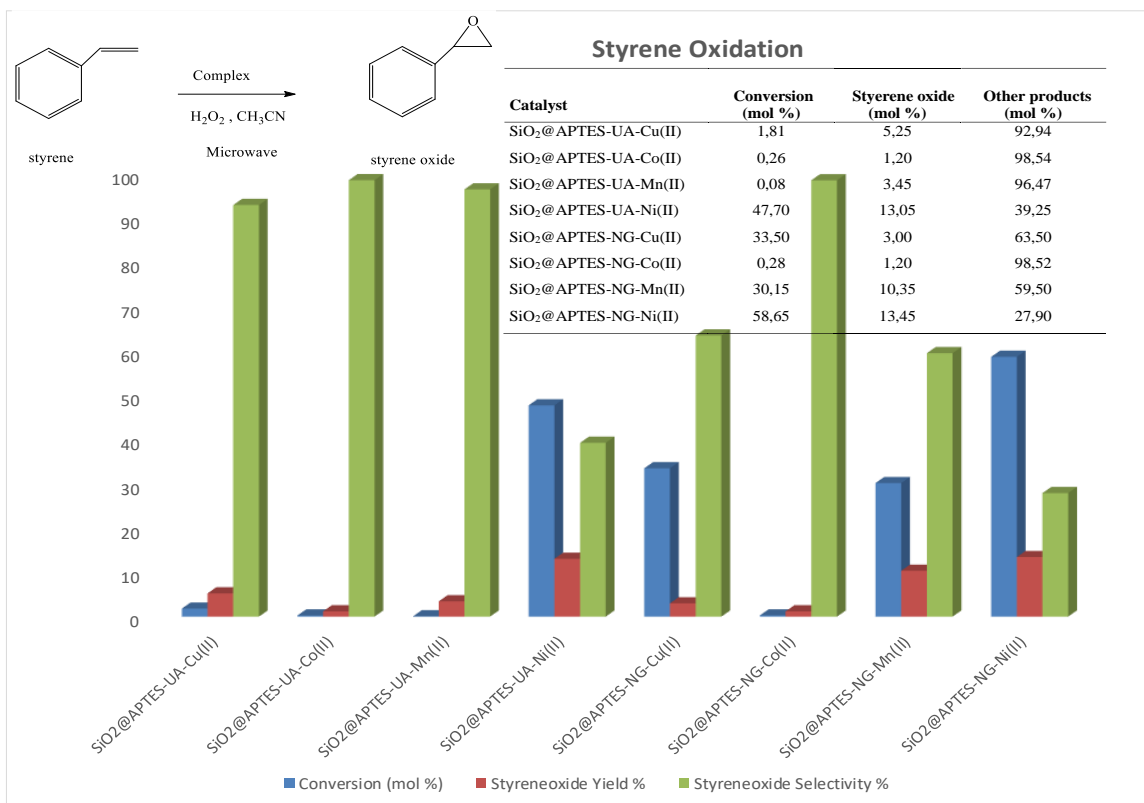


Fig. 4: The results of the catalytic oxidation.

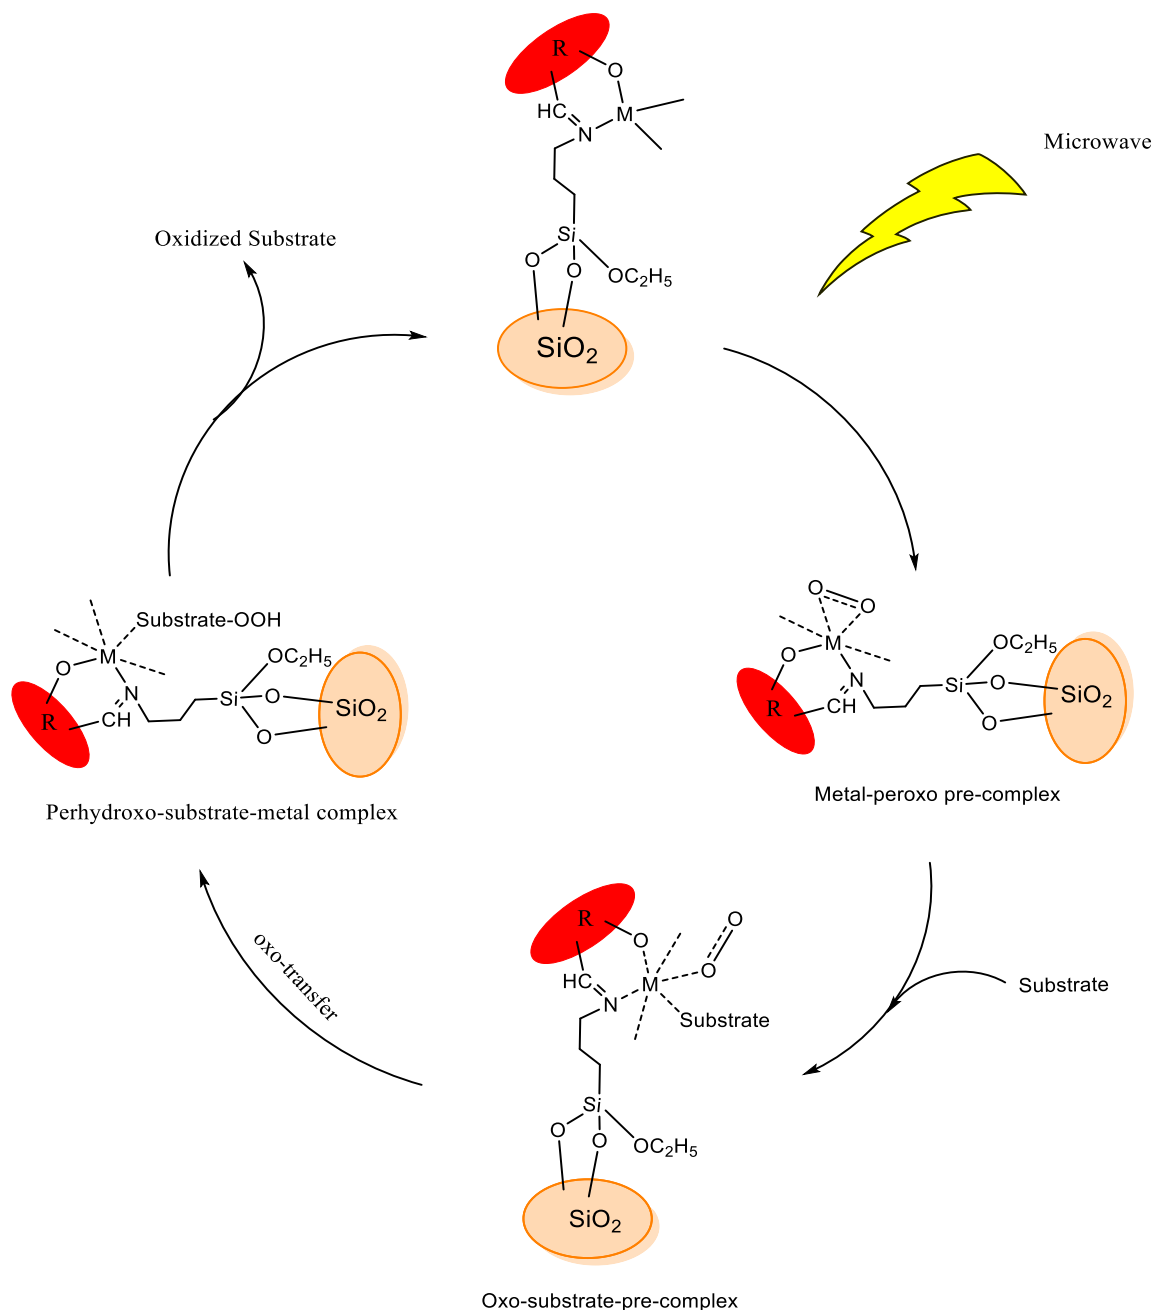


Fig. 5: Possible catalytic oxidation mechanism.

The tetra-coordinated metal complexes can be formed to octahedral geometries due to having two coordination holes which possibly accelerate the peroxo and the substrate coordinations. The pre-octahedral structure can control the oxidation mechanism like a processor. According to the possible oxidation reaction mechanism; firstly, peroxo ligand and the substrates were coordinated to the metal centers. Then, the obtained octahedral structure could be possibly evolved to the trigonal prismatic

molecular geometry. The trigonal prismatic molecular geometry having metal-peroxo and substrate attached pre-complexes accelerated the transfer of activated oxygen species to the substrates (Fig. 5). Microwave power was possibly accelerate the pre-oxo-substrate complexes and the forming of oxidized products coordinated to the metal centers. Possibly, tetrahedrally-coordinated Cu(II) complexes may be changed into different geometries. This flexible structure can provide the substrate and the

oxo species coordination in the reaction mechanism.

The major catalytic oxidation products of cyclohexene are cyclohexene oxide, 2-cyclohexen-1-one and 2-cyclohexen-1-ol. According to GC-FID results, the catalytic conversion of cyclohexene is around 50% (Fig. 4). All the complexes show good selectivity to 2-cyclohexen-1-ol especially Mn(II) complexes. Possibly, having different coordination structures of Mn(II), give important features of Mn(II) complexes in the oxidation mechanism of cyclohexene. These conversion rates are higher than the previous reports [2,27,35]. In particular, the metal complexes of the SiO₂@APTES-UA and SiO₂@APTES-NG ligands act as good catalysts in the synthesis of 2-cyclohexen-1-ol. Based on the GC-FID results summarized in (Fig. 4), cyclooctane were oxidized further by using the synthesized catalysts. SiO₂@APTES-UA-Mn(II) complex showed very good catalytic activity with 60.35% selectivity of cyclooctanone [2,27,35]. The present results show that the synthesized metal complexes are not efficient and selective enough catalysts in the cyclooctane oxidation. The conversion of styrene to styrene oxide using the synthesized catalysts is remarkable considering SiO₂@APTES-UA-Ni(II), SiO₂@APTES-NG-Ni(II) and SiO₂@APTES-NG-Mn(II) complexes [2]. Possibly, Ni(II) and Mn(II) complexes having different coordination structures give important features of in the oxidation mechanism of an organic substrates.

Conclusions

In this study, two new semi-synthetic silica-supported ligands with usnic acid and naringenin and their Cu (II), Ni (II), Mn (II) and Co (II) complexes were synthesized. The chemical structure of the new ligands and their metal complexes were characterized by FT-IR, TG/DTA, SEM, EDX, ICP-OES and elemental analysis methods. The extraction and pre-concentration of heavy metals from water by use of silica gel modified with different organic compounds as column fillers is well known in the literature[4,7,28,32–34]. Even some of the toxic metal ions have been recovered by 100%. These results showed that natural SiO₂@APTES-UA and SiO₂@APTES-NG solid phases are good heavy metal ion adsorbents. The synthesized complexes have been shown to exhibit heterogeneous catalytic properties on the oxidation of cyclohexane, cyclohexene and styrene, except for the cyclooctane oxidation. However, the catalytic properties of the metal complexes differed from each other due to the different oxidation properties of the metal ions used.

[9,10,27]In particular, Cu(II) and Co(II) complexes of the ligands are known to be active in the oxidation reactions and these results are agreement with the present results. In the view of the present results, significant contributions have been made to literature.

Acknowledgements

We would like to thank The Scientific & Technological Research Council of Turkey (TÜBİTAK) (Project No.: 111T211) and Kahramanmaraş Sütçü İmam University (Project No: 2017/1-82 M, 2018/2-2 YLS, 2018/2-18 YLS) for their financial supports.

References

1. M. Dolaz, M. Tümer, Synthesis, Spectroscopic Characterization and Properties of New Metal Complexes, *Transit. Met. Chem.*, **29**, 516 (2004).
2. Ö. F. Öztürk, Synthesis, Spectral, SEM, Antibacterial and Antifungal Activity Studies on Some Co(II), Ni(II) and Cu(II) Complexes of New Schiff Base, 4-[(E)-[(2-hydroxynaphthalen-1-yl)methylidene]amino]-N-(5-methyl-1,3,4-thiadiazol-2-yl)benzene sulfonamide, *J. Chem. Soc. Pak.*, **40**, 191 (2018).
3. M. Dolaz, V. McKee, S. Uruş, N. Demir, A.E. Sabik, A. Gölcü, M. Tümer, Synthesis, structural characterization, catalytic, thermal and electrochemical investigations of bidentate Schiff base ligand and its metal complexes, *Spectrochim. Acta Part A Mol. Biomol. Spectrosc.*, **76**, 174 (2010).
4. S. Uruş, M. Karabörk, H. Köksal, Synthesis, characterization and solid-phase extraction properties of novel bis(diazo-azomethine) ligands supported on mesoporous silica, *Appl. Organomet. Chem.*, **32**, (2018).
5. S. Uruş, M. Dolaz, M. Tümer, Synthesis and Catalytic Activities of Silica-Supported Multifunctional Azo-Containing Schiff Base Complexes with Cu(II), Co(II), Ni(II) and Mn(II), *J. Inorg. Organomet. Polym. Mater.*, **20**, 706 (2010).
6. S. Uruş, H. Adigüzel, M. Incesu, Synthesis of novel N4O4 type bis(diazoimine)-metal complexes supported on mesoporous silica: Microwave assisted catalytic oxidation of cyclohexane, cyclooctane, cyclohexene and styrene, *Chem. Eng. J.*, **296**, 90 (2016).
7. S. Uruş, S. Purtaş, G. Ceyhan, T. Erkenez, Highly effective solid phase extraction of some heavy metal ions using a cartridge filled with imprinted silica-supported N4O4 type bis(diazoimine) ligands, *Sep. Purif. Technol.*, **118**, 432 (2013).

8. K.N. Kumar, R. Ramesh, Synthesis, characterization, redox property and biological activity of Ru(II) carbonyl complexes containing O,N-donor ligands and heterocyclic bases, *Spectrochim. Acta Part A Mol. Biomol. Spectrosc.*, **60**, 2913 (2004).
9. S.A. Mohand, A. Levina, J. Muzart, Pyridinium Dichromate-Assisted Oxidative Cleavage of α -Functionalized Benzylic Alcohols by Sodium Percarbonate Under Phase-Transfer Conditions, *Synth. Commun.*, **25**, 2051 (1995).
10. M.K. Singh, S.N. Dubey, J.P. Tandon, Synthesis and Structural Studies of Tin(IV) Complexes with Bifunctional Tridentate Semi- and Thiosemicarbazones, *Synth. React. Inorg. Met. Chem.*, **23**, 1251 (1993).
11. M. Liu, Y. Wang, W. Wangyang, F. Liu, Y. Cui, Y. Duan, M. Wang, S. Liu, C. Rui, Design, Synthesis, and Insecticidal Activities of Phthalamides Containing a Hydrazone Substructure, *J. Agric. Food Chem.*, **58**, 6858 (2010).
12. J. Vančo, O. Švajlenová, E. Račanská, J. Muselik, J. Valentová, Antiradical activity of different copper(II) Schiff base complexes and their effect on alloxan-induced diabetes, *J. Trace Elem. Med. Biol.*, **18**, 155(2004).
13. R. Amin, B. Krammer, N. Abdel-Kader, T. Verwanger, A. El-Ansary, Antibacterial effect of some benzopyrone derivatives, *Eur. J. Med. Chem.*, **45**, 372 (2010).
14. Y.S. Higasio, T. Shoji, Heterocyclic compounds such as pyrroles, pyridines, pyrrolidins, piperdines, indoles, imidazol and pyrazins, *Appl. Catal. A Gen.*, **221**, 197 (2001).
15. N. Turan, M. Şekerci, Synthesis And Characterization Of Co (II), Ni (II), Cd (II) and Cu (II) Complexes Of Bis-Schiff Bases Obtained From 1,8-Diaminonaphthalene, *J. Chem. Soc. Pak.*, **31**, 564 (2009).
16. R. Gupta, D. Sharma, S. Singh, Eco-Friendly Synthesis and Insecticidal Activity of Some Fluorinated 2-(N-Arylamino)-4-Arylthiazoles, *Phosphorus. Sulfur. Silicon Relat. Elem.*, **185**, 1321 (2010).
17. A. Chaudhary, S.C. Joshi, R.V. Singh, Investigations on New Revolutionary Plant Growth Regulators and Fertility Inhibitors Tetraazamacrocyclic Complexes of Lead(II), *Main Gr. Met. Chem.*, **30**, 157 (2007).
18. A.A. Farag, E.M. Khalifa, N.A. Sadik, S.Y. Abbas, A.G. Al-Sehemi, Y.A. Ammar, Synthesis, characterization, and evaluation of some novel 4(3H)-quinazolinone derivatives as anti-inflammatory and analgesic agents, *Med. Chem. Res.*, **22**, 440 (2013).
19. S.M. Sondhi, S. Arya, R. Rani, N. Kumar, P. Roy, Synthesis, anti-inflammatory and anticancer activity evaluation of some mono- and bis-Schiff's bases, *Med. Chem. Res.*, **21**, 3620 (2012).
20. P.J. Blower, Small coordination complexes as radiopharmaceuticals for cancer targeting, *Transit. Met. Chem.*, **23**, 109 (1997).
21. T.A.K. Al-Allaf, L.J. Rasha, A. Stelzner, D.R. Powell, Organotin(IV) complexes with various donor ligands and their cytotoxicity against tumour cell lines. Part(I): R₂SnCl₂ with Schiff bases; unusual C=N bond cleavage of the bases and X-ray structures of the ionic products formed, *Appl. Organomet. Chem.*, **17**, 891 (2003).
22. S.R. Popuri, Y. Vijaya, V.M. Boddu, K. Abburi, Adsorptive removal of copper and nickel ions from water using chitosan coated PVC beads, *Bioresour. Technol.*, **100**, 194 (2009).
23. N. V Deorkar, L.L. Tavlarides, Zinc, Cadmium, and Lead Separation from Aqueous Streams Using Solid-Phase Extractants, *Ind. Eng. Chem. Res.*, **36**, 399 (1997).
24. J. Haginaka, Selectivity of affinity media in solid-phase extraction of analytes, *TrAC Trends Anal. Chem.*, **24**, 407 (2005).
25. E.A. Kazantsev, V.P. Remez, Sorption materials on carriers in water treating procedures, *Khimiya i Tekhnologiya Vody*, **17**, 50 (1995).
26. A. Baçaoui, A. Yaacoubi, A. Dahbi, C. Bennouna, R. Phan Tan Luu, F.J. Maldonado-Hodar, J. Rivera-Utrilla, C. Moreno-Castilla, Optimization of conditions for the preparation of activated carbons from olive-waste cakes, *Carbon*, **39**, 425 (2001).
27. C.H. Bartholomew, R.J. Farrauto, Fundamentals of Industrial Catalytic Processes, Wiley, p. 560 (2011).
28. S. Uruş, S. Purtaş, G. Ceyhan, F. Tümer, Solid phase extraction of Pb(II), Cu(II), Cd(II) and Cr(III) with syringe technique using novel silica-supported bis(diazoimine) ligands, *Chem. Eng. J.*, **220**, 420 (2013).
29. S. Koçer, S. Uruş, A. Çakır, M. Güllüce, M. Dıġrak, Y. Alan, A. Aslan, M. Tümer, M. Karadayı, C. Kazaz, H. Dal, The synthesis, characterization, antimicrobial and antimutagenic activities of hydroxyphenylimino ligands and their metal complexes of usnic acid isolated from *Usnea longissima*, *J. Chem. Soc. Dalton Trans.*, **43**, 6148 (2014).
30. S. Huneck, I. Yoshimura, Identification of Lichen Substances BT-Identification of Lichen Substances, in: S. Huneck, I. Yoshimura (Eds.), Springer Berlin Heidelberg, Berlin, Heidelberg, p. 11 (1996).

31. S. Oh, T. Kang, H. Kim, J. Moon, S. Hong, J. Yi, Preparation of novel ceramic membranes modified by mesoporous silica with 3-aminopropyltriethoxysilane (APTES) and its application to Cu²⁺ separation in the aqueous phase, *J. Memb. Sci.*, **301**, 118 (2007).
32. M. Soylak, S. Saracoglu, L. Elci, Sorbent extraction of some metal ions on a gas chromatographic stationary phase prior to their flame atomic absorption determinations, *Bull. Korean Chem. Soc.*, **24**, 555 (2003).
33. N. Tokman, S. Akman, M. Ozcan, U. Koklu, Preconcentration and separation of copper(II), cadmium(II) and chromium(III) in a syringe filled with 3-aminopropyltriethoxysilane supported on silica gel, *Anal. Bioanal. Chem.*, **374**, 977 (2002).
34. C. Xiong, X. Chen, X. Liu, Synthesis, characterization and application of ethylenediamine functionalized chelating resin for copper preconcentration in tea samples, *Chem. Eng. J.*, **203**, 115 (2012).
35. X.-H. Lu, Q.-H. Xia, H.-J. Zhan, H.-X. Yuan, C.-P. Ye, K.-X. Su, G. Xu, Synthesis, characterization and catalytic property of tetradentate Schiff-base complexes for the epoxidation of styrene, *J. Mol. Catal. A Chem.*, **250**, 62 (2006).